

SPECIFICATION CONTROL DRAWING

55/0312

TITLE	WIRE, RADIATION-CROSSLINKED MODIFIED ETFE INSULATED, ULTRA LIGHTWEIGHT, OUTER SPACE, 600 VOLT	Date	1-30-06	Revision	J
-------	--	------	---------	----------	---

This specification sheet forms a part of the latest issue of Raychem Specification 55/.

CONDUCTOR - SILVER-COATED COPPER

INSULATION - LOW OUTGASSING
RADIATION-CROSSLINKED,
MODIFIED ETFE

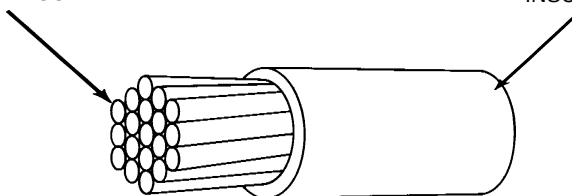


TABLE I. CONSTRUCTION DETAILS

PART NUMBER 1/	WIRE SIZE (AWG)	CONDUCTOR STRANDING (number x AWG)	DIAMETER OF STRANDED CONDUCTOR (in.)		FINISHED WIRE		
			MINIMUM	MAXIMUM	MAXIMUM RESISTANCE AT 20°C (ohms/1000 ft.)	DIAMETER (in.)	MAXIMUM WEIGHT (lbs/1000 ft.)
55/0312-28-*	28	7 x 36	.0140	.0150	63.8	.0225 ± .0015	.81
55/0312-26-*	26	19 x 38	.0175	.0191	38.4	.0274 ± .0017	1.22
55/0312-24-*	24	19 x 36	.0225	.0241	24.3	.0322 ± .0017	1.80
55/0312-22-*	22	19 x 34	.0285	.0301	15.1	.0390 ± .0017	2.70
55/0312-20-*	20	19 x 32	.0365	.0385	9.19	.0495 ± .0017	4.27
55/0312-18-*	18	19 x 30	.0452	.0476	5.79	.0590 ± .0017	6.56
55/0312-16-*	16	19 x 29	.0514	.0538	4.52	.0665 ± .0019	8.33
55/0312-14-*	14	19 x 27	.0644	.0674	2.88	.0810 ± .0021	12.81
55/0312-12-*	12	37 x 28	.0825	.0865	1.90	.1000 ± .0026	19.71
55/0312-10-*	10	37 x 26	.1050	.1090	1.19	.1260 ± .0040	31.70

TABLE II. PERFORMANCE DETAILS

BEND TESTING		
PART NUMBER 1/	MANDREL DIAMETER (inch) (± 3%)	WEIGHT (lb) (± 3%)
	CROSSLINK VERIFICATION	CROSSLINK VERIFICATION
55/0312-28-*	.250	.063
55/0312-26-*	.375	.063
55/0312-24-*	.375	.125
55/0312-22-*	.500	.188
55/0312-20-*	.500	.250
55/0312-18-*	.500	.250
55/0312-16-*	.750	.375
55/0312-14-*	1.00	.500
55/0312-12-*	1.50	.750
55/0312-10-*	2.00	.750

WIRE RATINGS AND ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 200°C

Maximum continuous conductor temperature

VOLTAGE RATING: 600 volts (rms) at sea level

CROSSLINK VERIFICATION: 300 ± 3°C for 1 hour

COLOR: White preferred

CONCENTRICITY: 80% (minimum)

IDENTIFICATION AND COLOR STRIPING DURABILITY:

125 cycles (250 strokes) (minimum), 500 g weight

INSULATION ELONGATION: 50% (minimum)

INSULATION FLAWS:

Spark Test, 1.5 kV (rms), (28 - 24 AWG)

3.0 kV (rms), (22 AWG & larger)

Impulse Dielectric Test, 6.0 kV (peak)

INSULATION THICKNESS: .004 in. (nominal)

RADIATION RESISTANCE: 500 megarads

SHRINKAGE: 230 ± 3°C for 1 hour, 0.125 in. (maximum) in 12 in.

VACUUM STABILITY:

Total Mass Loss (TML), 1.0% (maximum)

Volatle Condensable Material (VCM), 0.1% (maximum)

VOLTAGE WITHSTAND TEST (Post Environmental):

1500 volts (rms), 60 Hz, 5 minutes

PART NUMBER:

The "*" in the part numbers above shall be replaced
by color code designators.

1/ Example: AWG 20, white: 55/0312-20-9

Users should evaluate the suitability of this product for their application. Specifications are subject to change without notice.

Tyco Electronics also reserves the right to make changes in materials or processing, which do not affect compliance with any specification, without notification to Buyer.

1/ COLORS AND COLOR CODE DESIGNATORS SHALL BE IN ACCORDANCE WITH MIL-STD-681. OTHER CODES
AND SUFFIXES MAY BE ADDED TO THE PART NUMBER, AS NECESSARY, TO CAPTURE ANY ADDITIONAL
REQUIREMENTS IMPOSED BY THE PURCHASE ORDER.

tyco
Electronics

Raychem Wire & Cable
501 Oakside Avenue
Redwood City, CA 94063-3800
Phone: 1-800-227-8816
Fax: 1-650-361-6297

Данный компонент на территории Российской Федерации

Вы можете приобрести в компании MosChip.

Для оперативного оформления запроса Вам необходимо перейти по данной ссылке:

<http://moschip.ru/get-element>

Вы можете разместить у нас заказ для любого Вашего проекта, будь то серийное производство или разработка единичного прибора.

В нашем ассортименте представлены ведущие мировые производители активных и пассивных электронных компонентов.

Нашей специализацией является поставка электронной компонентной базы двойного назначения, продукции таких производителей как XILINX, Intel (ex.ALTERA), Vicor, Microchip, Texas Instruments, Analog Devices, Mini-Circuits, Amphenol, Glenair.

Сотрудничество с глобальными дистрибьюторами электронных компонентов, предоставляет возможность заказывать и получать с международных складов практически любой перечень компонентов в оптимальные для Вас сроки.

На всех этапах разработки и производства наши партнеры могут получить квалифицированную поддержку опытных инженеров.

Система менеджмента качества компании отвечает требованиям в соответствии с ГОСТ Р ИСО 9001, ГОСТ РВ 0015-002 и ЭС РД 009

Офис по работе с юридическими лицами:

105318, г.Москва, ул.Щербаковская д.3, офис 1107, 1118, ДЦ «Щербаковский»

Телефон: +7 495 668-12-70 (многоканальный)

Факс: +7 495 668-12-70 (доб.304)

E-mail: info@moschip.ru

Skype отдела продаж:

moschip.ru

moschip.ru_4

moschip.ru_6

moschip.ru_9